



Available online at <https://www.s-epub.in/>

# Pharma Research

An International Peer Reviewed, Indexed Journal  
10.62655/s-epub.2022.v14.i01.pp1-9

## EVALUATION OF FAMOTIDINE LOADED 3D-NANO-CELLULOSE NETWORK USED FOR ORAL ADMINISTRATION

VAN-HUNG MAI<sup>1</sup>, XUAN-THANH NGUYEN<sup>2</sup>,

### Affiliation

<sup>1</sup>Research Center for Anthropology and Mind Development, VNU University of Education, Vietnam,

<sup>2</sup>Institute of Scientific Research and Applications, Hanoi Pedagogical University 2,

### Article info

Published on: 12-03-2022

ISSN: 0975-8216

### Keywords:

Famotidine, Prolonged-release,  
Oral delivery

### ABSTRACT

In this study, we want to evaluate a three-dimensional nano-cellulose network (3DNC) that is loaded with famotidine and administered orally. A substance with nano-sized fibres,

3DNC is made from bacteria found in fermented green tea. It may load Famotidine into a sustained release treatment that improves medication absorption.

### INTRODUCTION

The 3DNC has properties such as high mechanical strength, very low density, and a structure made of very thin nanofibers. Based on the results of these investigations, 3DNCs may one day serve as delivery systems. According to research by Amin et al. [1], 3DNC membranes have the potential to enhance drug efficiency by extending the time it takes for the medication to be released. In simulated models, including the intestines and stomach, Huang L. et al. [2] managed the 3DNC's drug release. A low rate of berberine release was seen in acidic conditions, a normal rate in alkaline conditions, and a high rate in neutral pH conditions, according to the data obtained. Researchers Satishbabu B. K. et al. [3] studied the effects of Famotidine's slow-release medication rate on cod liver oil and calcium alginate granules. The gradual dissolution of Famotidine from

chitosan/sulfobutyl ether  $\beta$ -cyclodextrin composite tablets was investigated by Anraku M. et al. [4].

Zhu X. et al. [5] have studied the drug delivery system that increased the bioavailability of Famotidine in rats. Maday F. M. et al. [6] have evaluated the acid function of carboxymethyl-beta-cyclodextrin in improving the chemical stability, oral-route bioavailability, and bitter taste of Famotidine. Fahmy R. H. et al. [7] have tested the rate of release of Famotidine through the construction of liquisolid tablets in both *in vitro* and *in vivo*. Gao S. et al. [8] have studied the pharmacokinetics and bioavailability of Famotidine on 10 Chinese volunteers. The objective of study is the evaluation of Famotidine Loaded 3D-Nano-Cellulose Network three dimensional nano-cellulose network (3DNC) used for oral administration.

## MATERIALS AND METHODS

Materials and chemicals: Famotidine 99.5% (Sigma–The USA); tablets Famotidine (FAMSYN-20, Haryana–India); Dialysis bag (MWCO: 12000-14000; Serva–Germany); Yeast extract (USA); Peptone (European Union); Methanol, Acetonitrile, Sodium Acetate

Trihydrate, Triethylamine, Ice Acetic Acid,... (Merck); other standard

chemicals used in chromatography and analysis.

Laboratory Animal: healthy white rabbits, weight approximately 2.5-

2.7 kg, the same age, laboratory standard, is supplied from The National Institute of Drug Quality Control. The rabbits have adapted to laboratory conditions at least one week and have starveling in 12 h, supplied fully water during the preparation. Experiments on rabbits have been approved by the ethical committee for conduction the study, approval number: 458/Ministry of Health of Vietnam.

### Determine the physicochemical properties of 3DNC loaded famotidine

12h and 24h, take samples out to measure the spectral density of the samples. The samples were removed at every 5 ml intervals and adding again 5 ml of a buffer solution. The experiments were repeated three times for the mean value. The ratio of drug release is calculated according to the formula:

$$R\% = \frac{C_t \times V_1 + \sum_{i=1}^{t-1} C_i \times V_2}{m} \times 100$$

Where: R is the drug release ratio;  $C_t$  is the concentration of the solution at time t;  $V_1$  is the volume of buffer solution at different pH values; n are the number of samples taken from the solution of liberation;  $V_2$  is the volume of buffer added; m is the amount of drug absorbed into the 3DNC.

### Research the bioavailability of 3DNC loaded drug *in vivo*

Testing requirement: 12 laboratory rabbits divided into 4 groups (n=3 for each group).

The material structure 3DNC loaded drug by scanning electron microscope (SEM), in which the sample heat in 40 °C is in 20 min. The next step is to cover a thin platinum layer and then put it into the sample chamber.

Use the electron microscope FE-SEM Hitachi S-4800 with magnification  $M=20-800,000\times$ , resolution  $\delta = 1.0 \text{ NM}$  and piezoelectric accelerator  $U = 10\text{kV}$ .

Determine the interaction of 3DNC with the drug by the photo spectrometer Fourier transformation infrared (FT-IR): Samples are directly measured by reflectometry in 20 °C, moisture 40-43%.

### Research the drug release from 3DNC loaded drug *in vitro*

Drug dose, which was released through the delivery system was tested in buffer solution pH=2; 4.5; 6.8 [9]. According to the Pharmacopoeia of Vietnam [10]. Put 3DNC loaded drug in the dialysis bag, which is dipped in a buffer solution with specific pH (2; 4.5; 6.8) [10] during the night with a closed side, then add 5 ml buffer solution with pH levels respectively. Use Magnetic Stirrer, stirring speed 50 cycles/min, the temperature in range  $37 \text{ }^\circ\text{C} \pm 0.5 \text{ }^\circ\text{C}$ . After 0.5h; 1h; 1.5; 2h; 4h; 6h; 8h;

Every rabbit has given 1 capsule or 1 tablet with a single dose of 20 mg/rabbit: group 1 (commercial drugs), group 2 (3DNC-SM loaded drug), group 3 (3DNC-CM loaded drug) Group 4 (3DNC-RM loaded drug).

Sampling method: After the rabbits take the drugs, use blood samples taken from those rabbits before giving the drug (white drug without any medicine), then take blood in turn at 0.5h, 1h, 2h, 4h, 6h, 8h, 10h, 12h, and 24h after drug use [9]. Select suitable veins, the blood is collected behind the ear. Using a sterilized needle to aspirate the vein behind rabbit ears, blood in the test the tube contains anti-coagulants (EDTA). Only after taking the blood samples, was it gently inversed repeatedly to ensure well mixing with anticoagulants and immediately centrifuged at 5000 rpm for 10 min at 4 °C to separate the plasma. Floating plasma will be transferred to a clean tube and start to analyze [9].

Quantify  $F_a$  in blood plasma by high-

performance liquid chromatography (HPLC) method: Survey the chromatography condition, sampling process and evaluate the analytic technique based on our previous results.

### Assessing parameters bioavailability *in vivo*

Maximum concentration (C<sub>max</sub>): Maximum concentration exposes the intensity of interaction of drugs. The more absorbed the drug is, the

faster it reaches the maximum concentration. These concentrations must be higher than the minimum concentration to exhibit clinical responses. However, if the maximum concentration overtakes the safety threshold, the drug will be able to cause unwanted sides [11].

To evaluate bioavailability (BIOA), we use relative BIOA (formula 2.4) when the control products is an oral medication.

Where: AUC<sub>test</sub> is the curve area of testing drug; AUC<sub>standard</sub> is curve area of control drug; D<sub>test</sub> is the testing dose of the testing drug; D<sub>standard</sub> is the testing dose of control drug.

If the testing products have BIOA = 80-125% compared to the control products, it will be considered that is biological equivalence with the control products [11]. All results are analyzed, processed by Excel 2010, and the

pharmacokinetic parameters were calculated, processed by PK Solver software [12].


## RESULTS AND DISCUSSION

### Evaluate the release capacity of famotidine from 3DNC loaded drug *in vitro*

Conduct drug release *in vitro* from the 3DNC loaded materials under environmental conditions pH = 2; 4.5 and 6.8. The results of the drug release rate for the 3DNC types cultured in SM, CM, and RM loaded in the different pH media are shown in fig. 1. The results indicated that the 3DNC cultured in SM loaded drug after 12 h had a higher drug release rate at pH = 2 (88.79%) and pH = 4.5 (86.47%), lower than at pH = 6.8 (74.36%). At pH = 2 and pH = 4.5; the drug release rates from the 3DNC were cultured in SM slower but has a higher rate at pH = 6.8. After 12h, the drug release rate from the 3DNC in CM loaded drug has a high release rate of the Faat

$$\text{BIOA relative} = \frac{\text{AUC}_{\text{test}} \times \text{D}_{\text{standard}}}{\text{AUC}_{\text{standard}} \times \text{D}_{\text{test}}} \times 100$$

pH = 2 (88.11%) and at pH = 4.5 (89.99%), lower than pH = 6.8 (78.94%). The 3DNC cultured in CM loaded drug has been released at a faster rate at pH = 6.8 and releases less than the remaining pH. Just after 6 h, the 3DNC was cultured in RM loaded with the high acid release rate at pH = 2 (92.52%) and pH = 4.5 (93.19%), lower than at pH = 6.8 (83.69%). In the investigated pH, the 3DNC was cultured in RM loaded Fa having a fast and high rate of drug release.

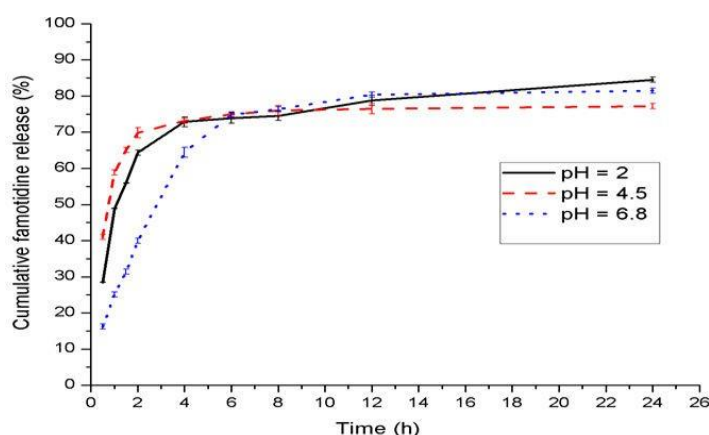


- a) 3DNC produced from SM loaded drug (n = 3), n: number of experiments; mean±SD: pH = 2 (62.1±0.29); pH = 4.5 (61.3±0.18); pH = 6.8 (55.2±0.34)

The results in fig. 1 stated that just after 6 h, commercial tablets Famotidine had a high rate of Fa release at pH = 2 (84.45%), lower than pH = 4.5 (78.16%) and pH = 6.8 (69.00%). At pH = 2, the rate of drug release from commercial tablets Fa was slower but higher than at pH = 4.5 and at pH = 6.8.


The comparison results of the pH effect on the drug release capacity of each drug-loaded 3DNC and of the commercial tablets Fa are shown in fig. 1. The results expressed that in highly acidic environments (pH =

2), each drug-loaded 3DNC, as well as the commercial tablets, had a higher Fa release rate than pH = 4.5 and pH = 6.8. This evidence may explain that Fa is well soluble in the acidic environment, so the drug will release better from the drug-loaded 3DNC as well as from the tablets. The result is consistent with other studies [2, 13].


The comparative results on the Fa release capacity of three drug-loaded 3DNC types and commercial tablets Fa in the media pH = 2; pH = 4.5 and pH = 6.8 was shown in fig. 2.

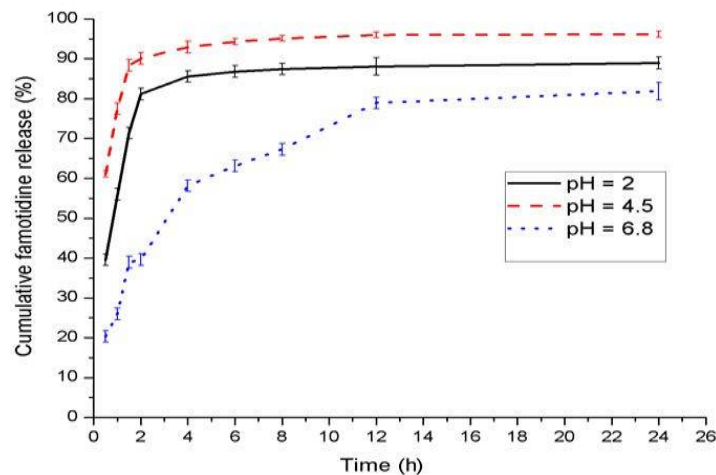

b) 3DNC produced from CM loaded drug (n = 3), n: number of experiments; mean±SD: pH = 2 (68.9±0.27); pH = 4.5 (89.1±0.84); pH = 6.8 (57.6±0.38)

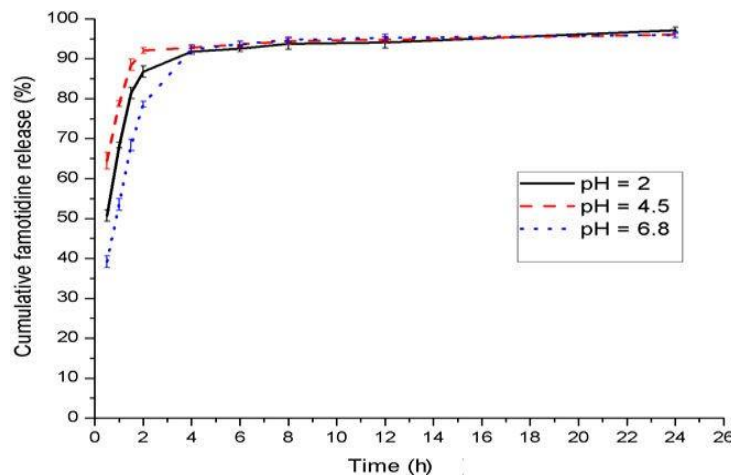


c) 3DNC produced from RM loaded drug (n = 3), n: number of experiments; mean±SD: pH = 2 (71.9±0.25); pH = 4.5 (83.5±0.18); pH = 6.8 (74.1±0.33)

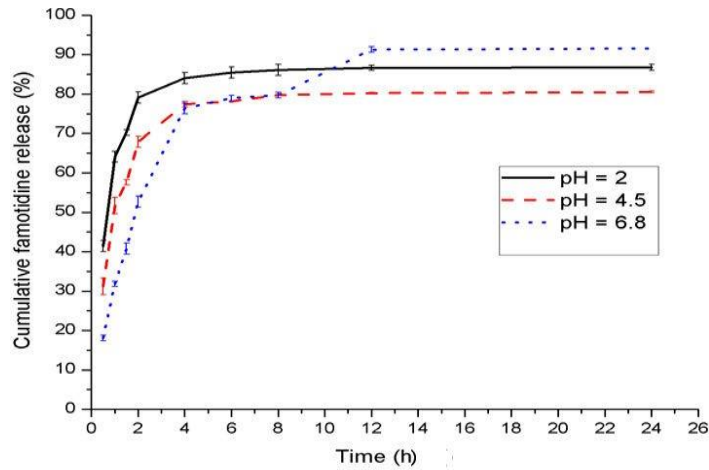


a) Commercial Famotidine tablets (n = 3), n: number of experiments; mean±SD: pH = 2 (56.4±0.14); pH = 4.5 (57.7±0.17); pH = 6.8 (62.6±0.39)


**Fig. 1: Percentage of Famotidine release from the 3DNC produced from SM, CM, and RM loaded drug in the different pH environments**

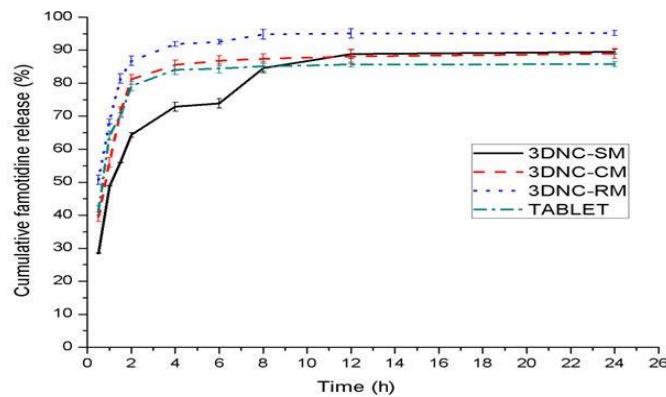

a) pH = 2 (n = 4), n: number of experiments; mean±SD: SM (66.7±0.33); CM (68.0±0.26); RM (74.6±0.30); TABLET (67.5±0.23)

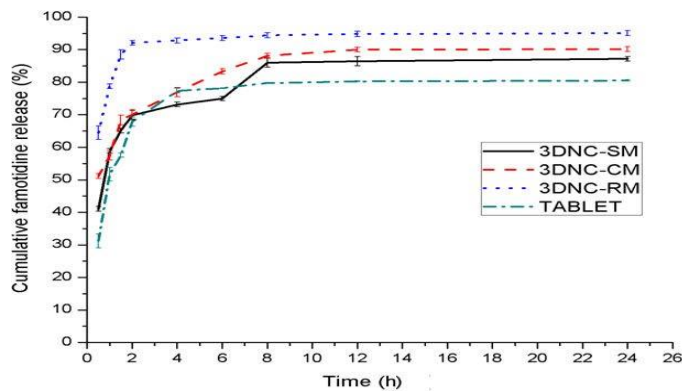

b) pH = 4.5; (n=4), n: number of experiments; mean±SD: SM (70.9±0.25); CM (75.6±0.22); RM (83.1±0.18); TABLET (61.6±0.28)

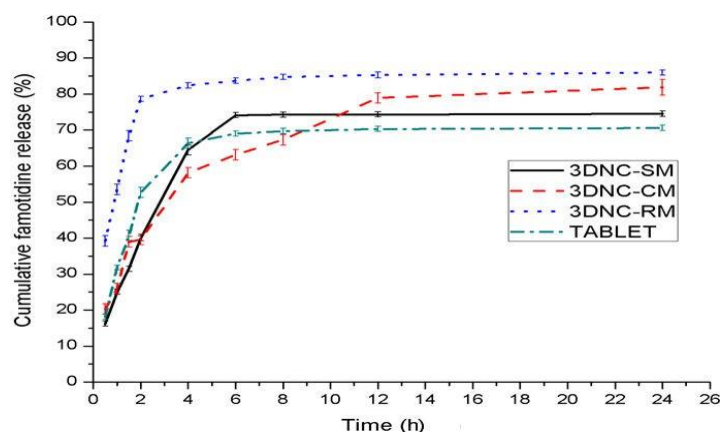

c) pH = 6.8; (n=4), n: number of experiments; mean±SD: SM (55.3±0.34); CM (58.6±0.33); RM (64.3±0.32); TABLET (57.7±0.24)

**Fig. 2: Percentage of Famotidine released from three 3DNC types loaded drug and commercial tablets Famotidine in distinct pH environments**

Research results showed that the 3DNC cultured in the drug-loaded SM with slow-release and slow-release catalysts, the 3DNC was cultured in CMs and tablets with medium release rates, whereas the 3DNC was cultured in RM loaded at a rapid release rate in the same pH = 2 medium. This can be explained by the SEM image showing that the size of the hole in the membrane is larger and that the number of holes is greater than the other ones, thus releasing the drug to the environment faster. This result is consistent with other studies [2].

Hence, in high acidic environments (pH = 2), each drug-loaded 3DNC, as well as the commercial tablets, had higher the pH release rates than at pH= 4.5 and pH = 6.8. The 3DNC cultured in drug- loaded SM has a slow and prolonged release, the 3DNC cultured in the drug-loaded CM and tablets have medium release rates, whereas the 3DNC cultured in the drug-loaded RM has a fast release in the same pH environment.

### **Evaluate bioavailability *in vivo* of famotidine release from 3DNC**

The analytic progress of Fa in the rabbit plasma was built, including sampling processes and analytical methods by HPLC. Throughout the survey, methanol solvent samples were selected, high- performance liquid chromatography conditions suitable for columns, mobile phases, detectors, flow rates, injection volumes allowed for Fa analysis in rabbit plasma with

a small detective limit of 0.0644µg/ml and a quantity limit of 0.212 µg/ml [14]. The Fa quantitative procedure in rabbit plasma has been evaluated for specificity, linearity, defined range, definite limit, quantitative limit, correctness, accuracy, precision. The results of the study show that the method is suitable for estimating Fa in rabbit plasma [14]. The

rabbit plasma samples obtained after oral administration of three doses of the drug-loaded 3DNC and Fa tablets with the same concentration of 20 mg/rabbit [15] were processed and quantified according to the

method described in our previous study [14]. The results of the Fa determination of rabbit plasma concentration after drinking the three types of 3DNC loaded drugs and the Fa tablets are shown in table 1.


**Table 1: Famotidine concentration in rabbit plasma after administering three types of the drug-loaded 3DNC and Famotidine tablets with the same concentration 20 mg/rabbit (n = 3)**

Time (h)	3DNC-SM ( $\mu\text{g/ml}$ ) mean $\pm$ SD	3DNC-CM ( $\mu\text{g/ml}$ ) mean $\pm$ SD	3DNC-RM ( $\mu\text{g/ml}$ ) mean $\pm$ SD	Tablet ( $\mu\text{g/ml}$ ) mean $\pm$ SD
0.5	2.641 $\pm$ 0.154	5.641 $\pm$ 0.154	6.917 $\pm$ 0.292	6.479 $\pm$ 0.979
1	6.006 $\pm$ 0.278	8.567 $\pm$ 0.220	9.520 $\pm$ 1.565	11.860 $\pm$ 0.760
2	9.751 $\pm$ 0.286	9.504 $\pm$ 0.279	11.318 $\pm$ 0.656	14.015 $\pm$ 0.933
4	10.946 $\pm$ 0.146	10.687 $\pm$ 0.082	12.972 $\pm$ 0.526	9.931 $\pm$ 0.711
6	11.723 $\pm$ 0.138	11.410 $\pm$ 0.190	11.518 $\pm$ 0.332	7.887 $\pm$ 1.068
8	11.274 $\pm$ 0.086	10.604 $\pm$ 0.102	6.410 $\pm$ 0.456	4.364 $\pm$ 0.463
10	8.906 $\pm$ 0.465	8.037 $\pm$ 0.182	3.974 $\pm$ 0.245	2.666 $\pm$ 0.319
12	5.804 $\pm$ 0.244	4.761 $\pm$ 0.288	2.689 $\pm$ 0.343	0.933 $\pm$ 0.218
24	0.834 $\pm$ 0.047	0.517 $\pm$ 0.277	0.207 $\pm$ 0.103	0.031 $\pm$ 0.006

(n: number of experiments)

The results in table 1, indicated that, at the early time of the survey, the rabbit plasma concentrations increased slowly in the rabbits using the 3DNC cultured from SM or the 3DNC cultured from CM but increased rapidly when the rabbits using the 3DNC cultured from drug-loaded RM or commercial tablets Fa. Almost all of the time, the Fa concentrations in the rabbit plasma using drug-loaded membranes are higher than the rabbits taking commercial tablets.

To better illustrate the differences in plasma concentrations of Fa among four groups of rabbits, the data were expressed as a mean of the curve of Fa concentration following the time (fig. 3).

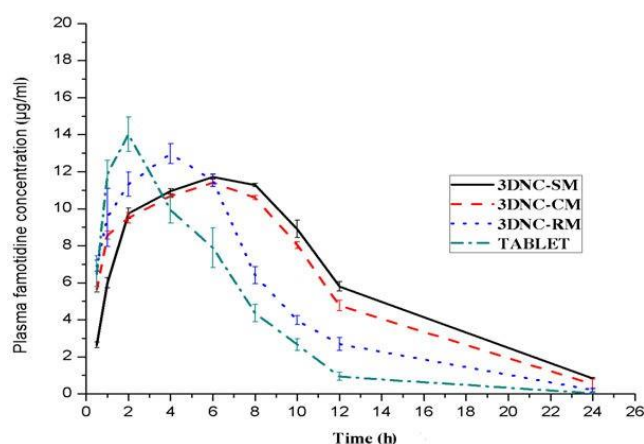

**Fig. 3: Expressing famotidine concentrations in rabbit plasma following the time (n=4), n: number of experiments; mean $\pm$ SD: SM (7.9 $\pm$ 0.48); CM (8.7 $\pm$ 0.30); RM (9.3 $\pm$ 0.35); TABLET (10.1 $\pm$ 0.35)**

**Table 2: Average pharmacokinetic parameters of three 3D-nano-cellulose structural network and commercial tablets famotidine (n= 4)**

Parameter	Unit	3DNC cultured from SM	3DNC cultured from CM	3DNC cultured from RM	Tablet
T <sub>max</sub>	hour	6	6	4	2
C <sub>max</sub>	ug/ml	11.72	11.41	12.97	14.02
t <sub>1/2</sub>	hour	4.21	3.64	3.27	2.24
AUC <sub>0-t</sub>	hour. ug/ml	152.44	142.82	119.12	91.19
AUC <sub>0-∞</sub>	hour. ug/ml	157.51	145.53	120.09	91.29

(n: number of experiments)

The indexes relating to the drug absorption by oral administration on rabbit groups taking the drug-loaded 3DNC types and commercial Fa tablets were shown in table 2.

The results in table 2, showed that the rabbits using the 3DNC cultured from SM, 3DNC cultured from CM, the 3DNC cultured from the RM loaded drug and commercial tablets Fa obtained C<sub>max</sub> after 6, 6, 4, 2 h, indicating that Fa in the commercial tablets is absorbed faster than the loaded Fa in the 3DNC types. Maximum drug concentrations in the plasma of the rabbits taking the drug-loaded 3DNC were loaded higher than the 3DNC cultured from the RM loaded drug. The *in vivo* bioavailability of drug-loaded 3DNC cultured in the standard media was 172%, the drug-loaded 3DNC in the coconut nutrient culture was 159%, the drug-loaded 3DNC in rice nutrient cultures were 131% compared to the tablets on the market. The drug-loaded 3DNCs have supports to improve the Fa bioavailability compared to commercial tablets. These results are similar to the study results assessing the Fa bioavailability in some other products [15].

## CONCLUSION

In strong acidic environments (pH=2), the 3DNC was cultured in SM with slow Famotidine release rate and extended-release (88.79% release rate) is the most effective one. Experiment on rabbits showed that the drug-loaded 3DNCs could help to prolong the drug release, in which the extended-release time of the 3DNC cultured in SM and CM was higher than that of the 3DNC grown in RM. The 3DNC loaded drugs help improve Famotidine bioavailability compared to the commercial

lower than the rabbits taking the commercial Fa tablets. The half-life (t<sub>1/2</sub>) and the area under the curve (AUC) of drug-loaded 3DNCs were higher than the commercial Fa tablets. T<sub>max</sub> of the 3DNC cultured from SM and CM was higher than the 3DNC cultured from the drug-loaded RM and the commercial Fa tablets were the smallest T<sub>max</sub>. Thus, the types of 3DNC loaded drugs can help with the prolonged drug release, in which the extended-release time of 3DNC membrane cultured from SM and the 3DNC was cultured from CM

tablets.

## REFERENCES

1. Ahmad N. Amin and MCIM Bacterial Cellulose Film Coating for Drug Delivery: Physical, Chemical, and Thermal Characteristics and Their Relation to Drug Release 1. This information was last retrieved from the Sain Malaysiana database on 2012-08-31. Authors: Huang, Chen, and Thanh Xuan Nguyen. 3D networks made of nanocellulose for the delivery of controlled-release pharmaceuticals. *Journal of Mater. Chemistry B* 2013;1:2976–84.
3. Sandeep VR, Satishbabu BK, and Shurtinag R. Famotidine floating drug delivery system development and testing. *Indian Journal of Pharmaceutical Sciences*, 2010;6:738–74.

The authors of the article are Anraku, Hiraga, Iohara, Pipkin, and Uekama. Tables made of chitosan/sulfobutyl ether β-



cyclodextrin composites release famotidine slowly. *Journal of Pharmaceutical Science* 2015;487:142-7.

Authors: Zhu X, Zhang Z, Qi X, and Xing J. Increasing famotidine oral bioavailability in rats by the development of cooperative minitables containing several units of floating bioadhesive. The citation for this article is *Drug Delivery* 2014;6:459-66.

6. Manayomi, Khaled, Yamasaki, Iohara, Taguchi, Anraku, et al. Chemical stability, oral bioavailability, and bitter taste of famotidine were improved by evaluating carboxymethyl-beta-cyclodextrin with acid function. *Journal of Pharmaceutical Sciences*, 2010;397:1-8.

Seventh, Fahmy RH and Kassem MA. Improving the rate of famotidine dissolving by means of liquisolid tablet formulation: study in vitro and in vivo. *Europe Journal of Pharmaceutical and Biopharmaceutical Sciences*, 2008, 3, 993-503.

Section 8. Gao, Liu, Wang, and Gao XH. Ten healthy Chinese volunteers were studied to determine the pharmacokinetics and bioavailability of famotidine. *Yi Xue Bao Yong Guo Yao* 1991;3:195-8.

9. Nguyễn Xuân Thanh. Nanoliposomes encased in chitosan for the administration of berberin hydrochloride orally. *Journal of Materials Chemistry B* 2014; 2: 7149–59.

10. The Health Ministry. Publishing House of Hanoi, Vietnam: Pharmacopoeia Vietnam IV, 2009.

11. Clinical Pharmacokinetics by Tran Thị Thu Hang, published by Phuong Dong Publisher in 2009.

Xie S., Zhang Y., Huo M., and Zhou J. Access pharmacokinetic and pharmacodynamic data analysis in Microsoft Excel with this add-in programme. *Programmes for Computing Methods Biomed* (2010, 3:36–44).

13. People named Le Thi Phuong Thao, Vinh Bao, and Nguyen Thien Hai. A 40 mg pill of famotidine is prepared. *The American Journal of Medical Science*, 2014, 2, 72–7.

The authors of the article are Phung Thi Kim Hue, Phan Thi Huyen Vy, Bui Minh Thy, Nguyen Xuan Thanh, and Trieu Nguyen Trung. Assessment of famotidine concentrations in rabbit plasma using a

validated method. *Johns Hopkins University Press*, 2018;1066:46-50.

Mishra V. developed floating microballoons laden with famotidine and studied their pharmacokinetics. The international journal of pharmaceutical science published an article in 2012 with the DOI: 4:511–5.

2.